

Analysis by neutron activation analysis a some ancient ceramics from Romanian territories

Agata Olariu

National Institute for Physics and Nuclear Engineering

P.O.Box MG-6, 76900 Bucharest Magurele, Romania

February 5, 2008

1 Introduction

Ceramics is the most common archaeological material and therefore it is very used material by the historians to draw temporal and cultural characterisations. The importance of knowledge the the compositional scheme of the pottery is well known¹⁻⁵ although very rarely one can get important conclusions from the elemental analysis of the potsherds⁶⁻⁸.

In this paper we have analyzed samples of Neolithic ceramics from Cucuteni Scanteia - Vaslui county (History Museum from Iasi), and Neolithic and Dacian ceramics from Magurele - near Bucharest (collection of the Scholl from Magurele), Romania, by the method of neutron activation analysis (NAA).

In Table 1 it is presented the list of the analyzed ceramics samples.

2 Experimental method

The samples listed in the Table 1 have been analyzed by neutron activation analysis. We considered that the analysis should give an image of the bulk of the objects and therefore the surface of the shards was removed. Also we had into consideration the homogeneity of the samples and that the samples must be representative for the whole object. Samples of 10-30 mg of potsherds have been cut, weighted and wrapped individually in plastic foil. The samples of 10-30 mg have been irradiated at the rabbit system of VVR-S reactor of the NIPNE, Bucharest-Magurele, at a flux of 1.5×10^{12} neutrons/cm²·sec⁻¹, for a period of 30 minutes. A standard spectroscopic pure metallic copper was used as neutron flux standard. The radioactivity of the samples has been measured after a decay time of 1...20 h, and again after a decay time of 10...14 d. The measurements have been performed with a Ge(Li) detector, 135 cm³ coupled at PC with a MCA interface. The system gave a resolution of 2.4 keV at 1.33 MeV (⁶⁰Co). The following elements have been noticed: Fe, K, La, Mn, Na, Sc and Sm.

3 Results and discussions

In the Table 2 are given the results of the neutron activation analysis on the ancient potsherds from Cucuteni Scanteia and Magurele. The concentrations are given in ppm, and when the concentration was larger than 10,000 ppm the result was given in percents. The considered statistical errors have been for La, Mn, Na, Sc and Sm <5% and $\approx$ 10% for K and Fe. The diagram from the Fig. 1 describes the analyzed potsherds from the point of view of all considered elements in the samples. The minimum and maximum limits of the concentrations are shown for all observed elements. One can notice that the 2 compositional schemes are not completely separated and there are regions of interference

between Cucuteni group of the objects and Magurele group.

Searching an characteristic element or ratio of elements for a given region, we have noticed that the ratios Na/Mn, La/Sc and La/Sm could be considered representative and characteristic for a group of analyzed sherds. In Fig. 2a and Fig. 2b are shown the diagrams of the ratios of concentrations Na/Mn versus La/Sc, and respectively Na/Mn versus La/Sm, and one could observe a relative synchronozation of the analyzed objects on the provenance and culture on the mentioned ratios.

References

1. A. Aspinall, D. N. Slater, "Neutron activation analysis of medieval ceramics", *Nature* 217 (1968) 368
2. J. S. Olin and Ed. V. Sayre, "Trace analysis of English and American pottery of the american colonial period" *The 1968 Intern. Conference of Modern Trends in Activation Analysis* (1968) p. 207
3. N. Saleh, A. Hallak and C. Bennet, "PIXE analysis of ancient ordanian pottery", *Nuclear Instruments and Methods* 181 (1981) p. 527
4. Ed. Sayre, "Activation Analysis applications in art and archaeology", in *Advances in Activation Analysis*, eds. J.M.A. Lenihan, S.J. Thomson and V.P. Guinn, Academic Press, London, p.157
5. Ch. Lahanier, F.D. Preusser and L. Van Zelst, "Study and conservation of museum objects: use of classical analytical techniques", *Nuclear Instruments and Methos*, B14 (1986) p.2
6. Zvi Goffer, *Archaeological Chemistry, Chemical Analysis*, Vol. 55, eds. P.J. Elving J. D. Winefordner, John Wiley & Sons, p.108
7. I. Perlman and F. Assaro, "Deduction of provenience of pottery from trace element analysis", *Scientific Methods in Medieval Archaeology*, ed. R. Berger Univ. of California Press (1970) p.389
8. A. Millet and H. Catling, "Composition and provenance: a challenge", *Archaeometry*, Vol. 9 (1966) p.92

Table 1. List of archaeological ceramic objects from Cucuteni and Magurele analyzed by neutron activation analysis

Sample	Object	Provenance
CS1, CS2, ..., CS17	ceramic sherds	Cucuteni Scânteia, county Vaslui
CS18, CS19	pigments, clay ball	Cucuteni Scânteia
M1dac, M2dac, M3dac	ceramic sherds	Dacian, Magurele
M4neo, M5neo, M6neo	ceramic sherds	Neolithic Magurele

Table 2. Concentrations, ancient ceramics from Cucuteni-Scanteia and Magurele, by NAA. The results are given in ppm, and for concentrations larger than 10,000 ppm, the results are given in %

Sample	Manganese	Natrium	Potassium	Samarium	Lanthanum	Scandium	Iron
CS1	828	8450	3.1%	8.3	40	21	6.2%
CS2	834	6480	2.8%	7	39	18	7.0%
CS3	840	5790	2.2%	7.2	39	18	4.7%
CS4	728	7540	2.4%	9	36	17	3.9%
CS5	1030	9360	2.4%	10	37	17	5.9%
CS6	905	8380	3.3%	11	55	23	6.1%
CS7	1070	1.28%	4.1%	11	42	19	7.9%
CS8	375	7780	2.9%	8.2	42	18	5.1%
CS9	985	7460	3.0%	9.5	40	23	5.5%
CS10	764	9830	4.0%	10	31	20	7.7%
CS11	905	9430	3.4%	11.5	53	24	6.8%
CS12	1130	5880	3.1%	9.5	42	20	6.0%
CS13	1040	7310	3.3%	13	50	22	7.1%
CS14	1180	1.17%	3.2%	11	40	25	5.0%
CS15	608	4880	3.6%	9.3	43	26	7.6%
CS16	634	7050	3.2%	6	34	24	8.4%
CS17	607	8560	3.3%	10.5	44	19	6.2%
CS18	2460	5980	2.6%	7	30	18	31%
CS19	1.92%	5890	9050	4	35	6	3.5%
M1dac	873	1.59%	3.4%	13	60	23	6.0%
M2dac	697	1.61%	4.1%	15	70	21	6.2%
M3dac	955	1.5%	3.2%	13	60	22	9.3%
M4neo	479	1.4%	2.1%	9	34	14	5.0%
M5neo	583	1.5%	3.5%	11	44	19	7.2%
M6neo	405	1.4%	2.2%	9	38	15	6.4%

Fig. 2a. Diagrams Na/Mn - La/Sc and
b. Na/Mn -La/Sm
Antic Ceramics, by NAA


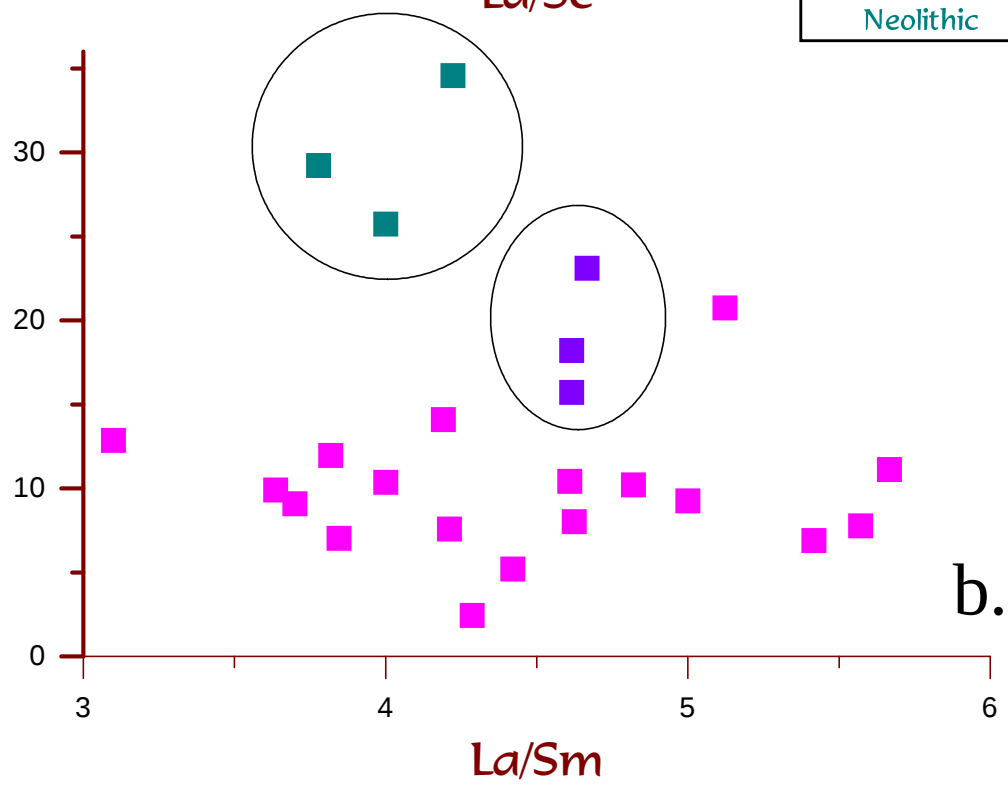


Fig. 2a. Diagrams Na/Mn - La/Sc and
b. Na/Mn -La/Sm
Antic Ceramics, by NAA

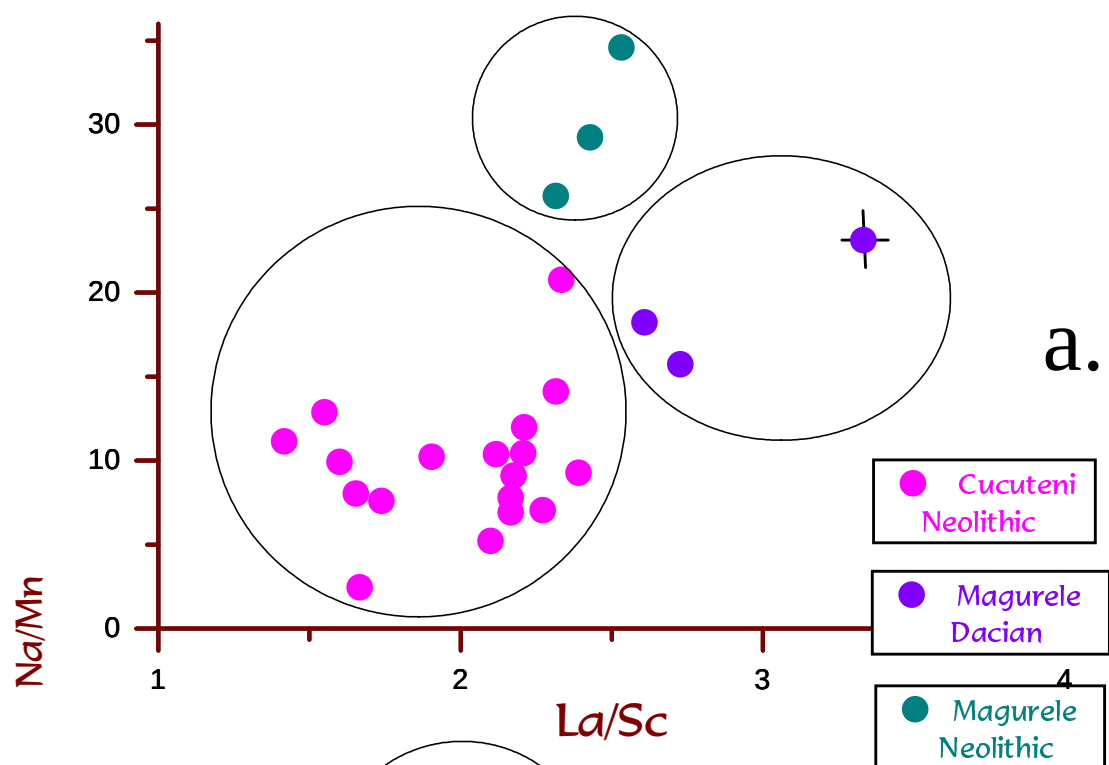